






VIASOL system data sheet

VIASOL **UNIVERSAL HBV SR**


Slip resistant, high chemical resistant epoxy resin based coating system, with hard-wearing and very good mechanical and chemical properties.

SYSTEM **BUILD-UP**

-  Top coat chemical resistant
VIASOL EP-C536 N
-  Wear coat chemical resistant broadcasted with natural quartz sand
VIASOL EP-C536 N
-  Scratch coat, levelling coating
VIASOL EP-C500 or EP-T703 (optional)
-  Primer for cementitious substrates:
VIASOL EP-P203, EP-T703 or other
-  Substrate: concrete, cementitious screed, others on request

SYSTEM **THICKNESS**

2.0 – 5.0 mm

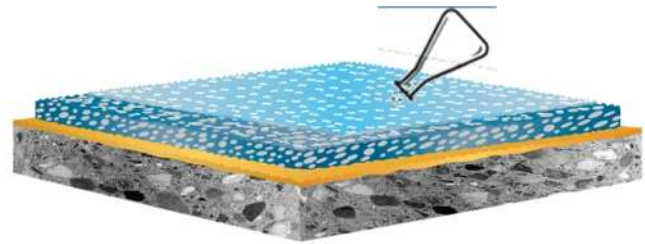

SYSTEM **HIGHLIGHTS**

- High wear resistance
- High chemical resistant against test liquids of the DiBT.
- Slip resistant surface

APPLICATION **FIELDS**

- Chemical and pharmaceutical industry
- Production areas with chemical loads
- Workshops
- Warehouses and high bay storage



SYSTEM **BENEFITS**

- Wear resistant, capable of bearing medium mechanical loads
- High abrasion and impact resistance
- Very good chemical resistance acc. to the test liquids of DiBT
- Hygienic, complies with regulations of EU food industry (ISEGA certified)
- Joint less, seam less
- Impermeable to liquids
- Slip resistant surface
- Good adhesion to concrete and other substrates, with special primers also suitable on substrates with rising water
- Slip resistant surface ca. R10 / R11 / R12
- Fire resistance class B_{fl}-s1

Manufacturer:

VIACOR Polymer GmbH, Graf-Bentzel-Str.78, D-72108 Rottenburg,
page 1/2

version no. 4

Tel: +49/7472-94999-0, info@viacor.de, www.viacor.de

issue: 04-2018

VIASOL system data sheet

VIASOL UNIVERSAL HBV SR

APPLICATION AND CONSUMPTION

layer	product	consumption (kg/m ²)	sand broadcasting (kg/m ²)	thickness mm	application
Self-levelling coating chemical resistant	VIASOL EP-C536 N	0.55 – 1.0	None	0.5 – 0.9	squeegee and finish with roller
Wear coat broadcasted with natural quartz sand	VIASOL EP-C536 N QS 0.3-0.8 mm or QS 0.6-1.2 mm	1.5 – 3.0	QS 0.3 – 0.8 mm or QS 0.6 – 1.2 mm in excess	2.5 – 5.5	notched trowel or squeegee
Scratch coat, levelling layer (optional)	VIASOL EP-C500 (fillable 10-30% with VIASOL QNV0)	0.5 – 2.0 + 0.05 – 0.6 QNV0	None	0.5 – 2.0	trowel or rubber squeegee / notched trowel or squeegee
alternative	VIASOL EP-T703 (fillable 50-100% with VIASOL QNV0)	0.5 – 2.0 + 0.25 – 1.0 QNV0	None	0.5 – 2.0	trowel or rubber squeegee / notched trowel or squeegee
Primer	VIASOL EP-P203 or VIASOL EP-T703	0.3 – 0.5	optional QS 0.3 – 0.8 mm	0.2 – 0.3	roller, squeegee + roller
Substrate	Cementitious substrates according to the appropriate standards and approvals must be capable of bearing loads and be free of cracks and voids. Pull-off strength ≥ 1.5 N/mm ² , residual moisture content < 4 %-CM, with higher residual moisture and on substrates with moisture from the backside special measures must be taken or a damp proof membrane must be installed. Substrate preparation e.g. grinding or shot blasting, sweeping and vacuum-cleaning is mandatory. Consumptions are calculated with VIASOL quartz sands and fillers. Usage of other quartz sands and fillers can cause changes of consumption and technical data.				
Note	Detailed application instructions are available upon request or refer to the technical product data sheet.				

TECHNICAL DATA

Property	standard	result
Slip resistance	DIN 51130 / ASR 1,5/1.2	R10 – R12
Shore-Hardness	EN ISO 868	D 60 after 28 d
Adhesive strength	EN ISO 4624	>2.0 N/mm ² (concrete failure)
Impact strength	EN 13813	≥ 4 Nm (IR4)
Wear resistance (Taber)	EN ISO 5470-1	≤ 75 mg
Solvent free / Total solid	Test method "Deutsche Bauchemie"	≤ 1 %
Chemical Resistance	EN ISO 2812-1	Test liquids DiBt: 3, 3b, 4, 4a, 4c, 5, 5a, 5b, 6, 6b, 7, 7a,7b, 8, 8a, 9, 9a, 10, 11, 12, 13, 14, 15a (more see chemical resistance list)
Fire Resistance (VIASOL WHG)	EN 13501-1	B _{ii} -S1

Remark: for further information please refer to the product data sheets or contact our technical service. All data are approximate values. Therefore no liability claims can be derived from the system data sheet. As all VIACOR data sheets are updated on a regular basis it is the users responsibility to obtain the most recent issue (see www.viacor.de or contact us directly)– all technical information is subject to change without prior notice

Manufacturer:

VIACOR Polymer GmbH, Graf-Bentzel-Str.78, D-72108 Rottenburg,
page 2/2

Tel: +49/7472-94999-0, info@viacor.de, www.viacor.de

version no. 4

issue: 04-2018